



Review Article

Accelerating electrochemistry with metal nanowires

Myung Jun Kim, Mutya A. Cruz, Feichen Yang and Benjamin J. Wiley



Abstract

Scalable, solution-phase syntheses of metal nanowires are enabling their increased use in electrochemical processes. This review highlights recent results demonstrating how metal nanowires can exhibit better durability and higher activity than traditional metal nanoparticle electrocatalysts on carbon supports. Metal nanowires can also form interconnected two-dimensional and three-dimensional (3D) networks that eliminate the need for a carbon support, thus eliminating the detrimental effects of carbon corrosion. Porous 3D networks of nanowires can be used as flow-through electrodes with the highest specific surface areas and mass transport coefficients obtained to date, enabling dramatic increases in the productivity of electrochemical reactions. Nanowire networks are also serving as 3D current collectors that improve the capacity of batteries. The tunable surface structure and dimensions of metal nanowires offer researchers a new opportunity to create electrodes that are tailored from the atomic scale to the microscale to improve electrochemical performance.

Addresses

Department of Chemistry, Duke University, 124 Science Drive, Box 90354, Durham, NC 27708, United States

Corresponding author: Wiley, Benjamin J. (benjamin.wiley@duke.edu)

Current Opinion in Electrochemistry 2019, 16:19–27

This review comes from a themed issue on **Electrochemical Materials and Engineering**

Edited by **Frank C. Walsh**

For a complete overview see the [Issue](#) and the [Editorial](#)

Available online 21 March 2019

<https://doi.org/10.1016/j.coelec.2019.03.005>

2451-9103/© 2019 Elsevier B.V. All rights reserved.

Keywords

Metal nanowires, Synthesis, Electrocatalyst, Flow-through electrode, Li battery.

Introduction

Metal nanowires are essentially sticks of metal with diameters on the order of 100 nm or less and lengths ranging from several to hundreds of microns. Some of the earliest nanowires were synthesized by electrodeposition in nanoporous aluminum oxide [1–3], but this method is difficult to scale. Around the turn of the

century, researchers discovered that anisotropic, crystalline nanowires could be grown from metals with symmetric, cubic crystal structures in a liquid solution, a technique referred to as solution-phase or colloidal synthesis [4]. This innovation allowed researchers to produce nanowires at a much larger scale than was previously possible [5–7], facilitating their use in a wide variety of applications. Today, metal nanowires can be produced from 23 different metals, including Ag [8,9], Au [10–13], Cu [14–17], Pd [18,19], Pt [20,21], Ni [22], and Pb [23,24]. The structure-dependent electrical, optical, and chemical properties of metal nanowires are being explored across a wide range of applications, including transparent conductors [25–27], wearable electronics [28,29], chemical/biological sensing and imaging [30–34], cancer therapy [30–32,35], waveguiding [36], and electrocatalysis [37–43]. The purpose of this review is to highlight recent results demonstrating the role nanowires can play in the advancement of electrochemical processes.

How nanowires grow—in brief

Solution-phase syntheses of metal nanowires start with the reduction or decomposition of a metal precursor, which results in the formation of small metal nanoparticles often referred to as a seed. Metal nanowires grow from seeds via atomic addition or particle attachment (Figure 1a). In atomic addition, the seed crystals grow into nanowires by continuous deposition of metal atoms at the ends of the growing nanocrystals. For example, atomic addition to the {111} facets on the faces of five-fold twinned decahedra (Figure 1b) [44] leads to the formation of nanowires (Figure 1c) [45] with pentagonal cross sections and five twin boundaries parallel to their longitudinal axis. As shown in Figure 1d, the sides of pentagonal nanowires are enclosed by five {100} surfaces, whereas the pentagonal ends are covered by {111} facets. It has generally been hypothesized that capping agents (e.g. polyvinylpyrrolidone for Ag [9] and hexadecylamine for Cu [14]) preferentially adsorb to and inhibit atomic addition to the sides of the nanowire, leaving the ends open to atomic addition. However, recent studies with Cu single-crystal electrodes revealed that this hypothesis is false for Cu nanowire growth [45,46]. In one case, it was shown ethylenediamine acted as a facet-selective promoter of Cu nanowire growth by removing surface oxide

57,60–62], oxygen evolution reaction [63,64], hydrogen evolution reaction [58,65–67], methanol/ethanol oxidation [59,68–76], formic acid oxidation [70,77–79], and CO₂ reduction [37,80,81].

Atomic structure

The twin boundaries on the side of pentagonally twinned nanowires (Figure 1d) and surface defects of nanowires grown via particle attachment (Figure 1f) can improve electrocatalytic performance [55,59,60,78,80,82]. Li et al [80] demonstrated how pentagonally twinned Cu nanowires improved the selectivity of CO₂ reduction (Figure 2). Unlike a polycrystalline Cu electrode that produced several products including methane, ethanol, and ethylene (e.g. ethylene: ~23%, methane: ~22%, H₂: ~21%, ethanol: ~10%, at the potential of -1.05 V vs. reversible hydrogen electrode (RHE)) [83], 95% of the product obtained using pentagonally twinned Cu nanowires was methane at a potential more negative than -1 V (vs. RHE) (Figure 2b) [80]. The Cu nanowires had a partial current for methane two times higher than Cu foils (Figure 2c). The higher methane selectivity was hypothesized to be due to a higher density of twin boundaries on the side of nanowires, which enhanced the binding of the intermediate for CO₂ reduction.


When CO₂ reduction was performed for longer times, the Cu nanowires lost their selectivity for methane and produced more ethylene (Figure 2d) because of the morphological degradation of Cu nanowires (Figure 2e). A coating of reduced graphene oxide on the Cu nanowires preserved the methane selectivity (Figure 2f) by inhibiting the morphological change of Cu nanowires (Figure 2g).

In another example, the rhombic atomic structure of jagged Pt nanowire surfaces increased the electrochemically active surface area (ECSA) 1.59 times compared with conventional Pt/C [55]. Its specific activity for ORR at 0.9 V (vs. RHE) was 7.2 times higher than that of smooth Pt nanowires and 32.9 times higher than that of Pt/C.

Alloyed nanowires

Alloying noble metals with non-noble metals is an effective approach to improve electrocatalytic performance through strain and ligand effects [84–87]. The addition of a non-noble metal can modify the electronic structure of noble metal nanowires and affect the binding strength of reactants, intermediates, and products, thereby improving electrocatalytic performance. A variety of alloyed nanowires including Pt- [52,54,56–

Figure 2

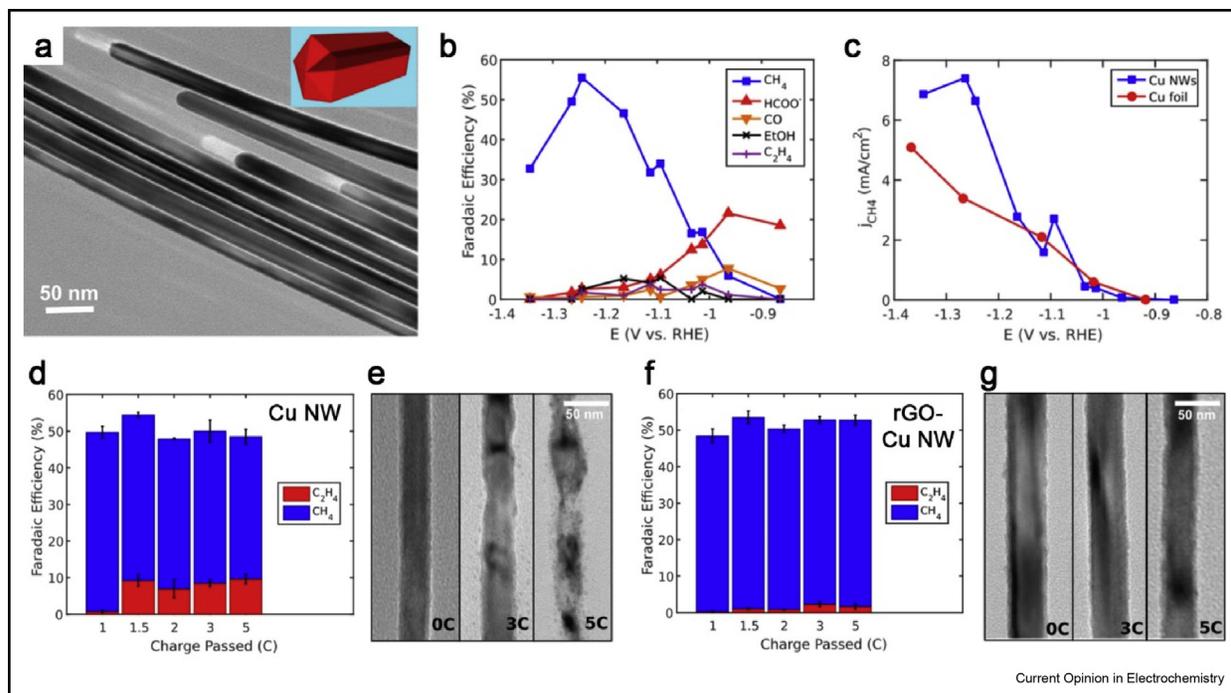

Pentagonally twinned Cu nanowires for CO₂ reduction. (a) Transmission electron microscopy (TEM) image of pentagonally twinned Cu nanowires for CO₂ reduction. (b) Faradaic efficiency for various products of CO₂ reduction on Cu nanowires and (c) a comparison of partial reduction current for methane from Cu nanowires and Cu foil. (d) Changes in Faradaic efficiency for methane and ethane and (e) the morphology of Cu nanowires (Cu NW) during CO₂ reduction. (f) Changes in Faradaic efficiency for methane and ethane and (g) the morphology of rGO-coated Cu nanowires (rGO-Cu NW) during CO₂ reduction. Reprinted with permission from Ref. [80]. Copyright 2017 American Chemical Society. rGO, reduced graphene oxide.

58], Pd- [68,69], Ir- [62,76], and Ni-based [66] nanowires have been adopted to improve various reactions.


In one example, PtNiRh trimetallic nanowires with an atomic ratio of 3.02:1.00:0.23 (Pt:Ni:Rh) were used for ORR (Figure 3) [57]. The PtNiRh nanowires grew in the $\langle 110 \rangle$ direction with $\{111\}$ side facets (Figure 3a–c) and had an average diameter of only 1 nm (Figure 3d). The ECSAs of Pt, PtNi, and PtNiRh nanowires were 74.7, 89.8, and 106.4 $\text{m}^2/\text{g}_{\text{Pt}}$, respectively. These ECSAs are all larger than that of commercial Pt/C (67.9 $\text{m}^2/\text{g}_{\text{Pt}}$) because of the thinner diameter and lower Pt–Pt coordination number of the alloyed nanowires. The specific activity, that is, catalytic activity per unit surface area, for ORR at 0.9 V (vs. RHE) was enhanced for the PtNiRh (2.71 mA/cm^2) and PtNi (2.34 mA/cm^2) nanowires compared with Pt/C (0.28 mA/cm^2) (Figure 3e). The activity enhancement was attributed to compressive strain and ligand effects from incorporating Ni and Rh into Pt, which reduced the binding strength of oxygenated species (Figure 3f). After 10,000 cycles of accelerated durability testing, the PtNiRh nanowires lost 12.8% of their initial mass activity. PtNi nanowires, Pt nanowires, and Pt/C lost 54.3%, 21.5%, and 73.7% of

their initial activity, respectively (Figure 3g). The greater durability of PtNiRh nanowires was attributed to the high energy required to form a Pt vacancy on PtNiRh(111) relative to PtNi(111) or Pt(111) (Figure 3h).

Hollow nanotubes

Another approach to boost electrocatalytic performance is to use hollow nanotubes which present more specific surface area for electrochemical reactions. Hollow nanotubes can be synthesized via galvanic displacement of nanowire templates [38,39,75,77,88]. In one recent report, PtRuTe and PtPdRuTe nanotubes were synthesized via galvanic displacement of Te nanowires [75]. The atomic composition of the nanotubes was easily controlled by changing the ratio of Pt and Pd precursors. The mass activity of the optimal PtPdRuTe nanotubes for methanol oxidation was 1261.5 $\text{mA}/\text{mg}_{\text{Pt}}$, which was 2.2 times higher than that of Pt/C. The ratio of the peak currents from the forward and backward scans was 20% higher for PtPdRuTe nanotubes than Pt/C, indicating the PtPdRuTe nanotubes were more resistant to poisoning from carbonaceous species [75].

Figure 3

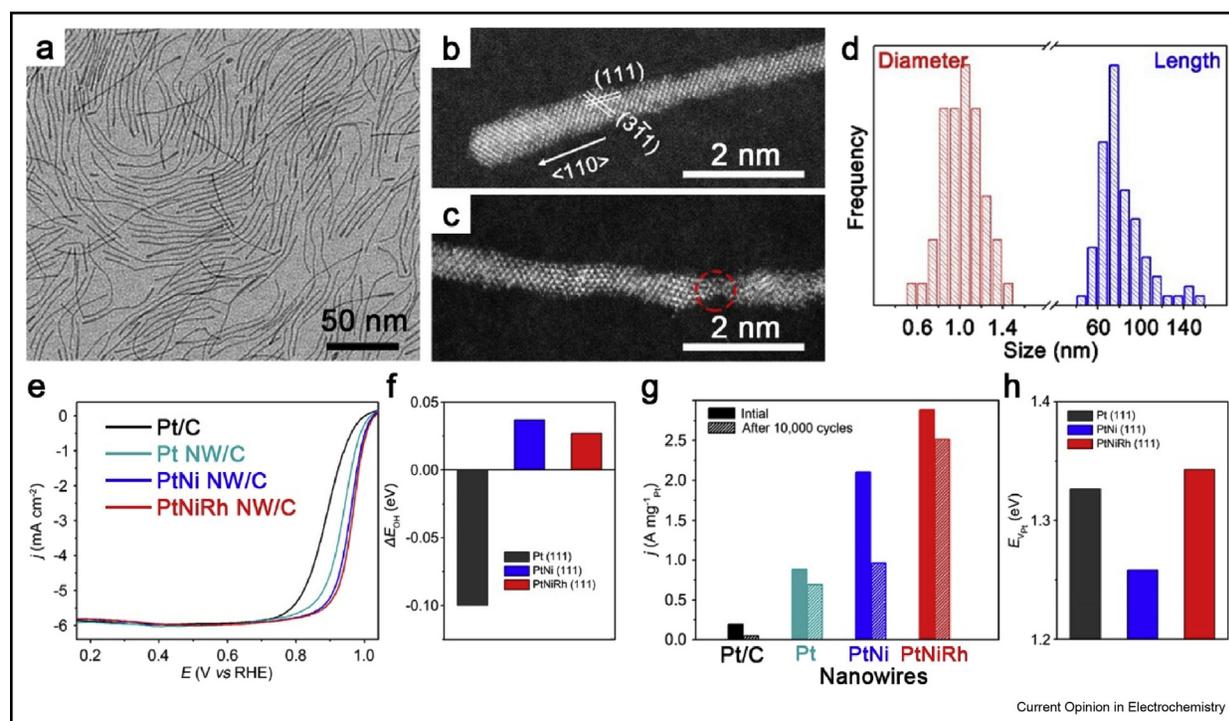

PtNiRh nanowires for the oxygen reduction reaction. (a–c) TEM images of PtNiRh nanowires. (d) The diameter and length of the PtNiRh nanowires. (e) Polarization curves for Pt/C, Pt nanowire/C, PtNi nanowire/C, and PtNiRh nanowire/C in O_2 -saturated HClO_4 solutions. (f) The binding energy of OH on Pt(111), PtNi(111), and PtNiRh(111). (g) The changes in the mass activity after durability testing. (h) The energy required for the formation of a Pt vacancy for Pt(111), PtNi(111), and PtNiRh(111). Reprinted with permission from Ref. [57]. Copyright 2018 American Chemical Society.

Self-supporting metal nanowires

Carbon is widely used as a conductive support for nanoparticle catalysts. However, carbon supports can be corroded during electrochemical processes, leading to the detachment of the electrocatalysts from the support [73,89,90]. The degradation of carbon supports can also produce CO when the electrode potential is more positive than 0.5 V (vs. RHE), accelerating the poisoning of the electrocatalysts [73,89,90]. Because metal nanowire networks do not require carbon supports to achieve high electrical conductivity, these problems can be avoided and better durability can be achieved [39,43,73,77,91,92]. In one example, a free-standing Pt nanowire membrane without carbon supports retained 82% of its initial ECSA, whereas Pt/C and Pt black catalysts retained only 5% and 39% of their initial ECSAs, respectively, after 3000 cycles of cyclic voltammetry [91]. The better stability of the Pt nanowire membrane was attributed to the absence of electrochemical carbon corrosion and the greater resistance of the Pt nanowires to Ostwald ripening compared with Pt/C.

Three-dimensional nanowire networks

The high aspect ratio of metal nanowires enables the fabrication of highly porous three-dimensional (3D) structures via filtration [28,93], ice-template freezing [94], electrodeposition [95,96], and drop casting [97]. In our experience, one of simplest ways of fabricating a nanowire-based porous electrode is filtration. The porosity (ϵ) of the nanowire felt made via filtration of stiff nanowires is determined by the aspect ratio of the nanowires, as described in the following equation [98].

$$\epsilon = 1 - \frac{2 \ln(\textit{Aspect ratio})}{\textit{Aspect ratio}} \quad (1)$$

Parkhouse and Kelly [98] and Kim et al. (M.J. Kim et al., ChemRxiv <https://doi.org/10.26434/chemrxiv.7468703.v1>) validated this equation experimentally using uncooked spaghetti and Cu nanowires, respectively. This equation predicts that nanowires with an aspect ratio of 100 will have a porosity of 91%. The large void fractions of nanowire felts, coupled with the small diameters of the nanowires, suggest they can be used as flow-through electrodes. Flow-through electrodes are used in redox flow batteries [99,100], water treatment [101], and chemical production [102–104] because of their high mass transport coefficients and large surface areas per unit volume. As the flow-through electrodes currently in use (e.g. carbon paper) were all introduced over 40 years ago, there may be room for improvement.

To quantify the performance of a flow-through electrode, one can measure its mass transport-limited current, I_L , by Eq. (1) [105–107].

$$I_L = nFA_r u C_0 \left[1 - \exp\left(-\frac{Lk_m A_s}{u}\right) \right] \quad (2)$$

Here n is the number of electrons required for the reaction, F is the Faraday constant, A_r is the cross-sectional area of the porous electrode, u is the superficial velocity, C_0 is the concentration of reactant at the inlet, L is the thickness of the porous electrode, k_m is the mass transport coefficient of the electrode, and A_s is the specific surface area of the electrode. I_L increases as $k_m A_s$ increases, so the higher the $k_m A_s$, the better the electrode.

Recent results demonstrate that replacing carbon fibers with Cu nanowires in a flow-through electrode increased the $k_m A_s$ up to 53.9 times at a superficial velocity of 0.5 cm/s (M.J. Kim et al., ChemRxiv <https://doi.org/10.26434/chemrxiv.7468703.v1>). At an electrode thickness of 1 cm, Eq. (2) predicts that the nanowire felt can accommodate a 10^5 times faster flow rate than carbon paper and obtain the same single-pass conversion of 0.9. However, a reaction will likely be limited by charge transfer kinetics before such high productivities can be achieved. Even with the current limited by charge transfer, a 278-fold increase in productivity for Cu ion reduction and a 4.24-fold increase in intramolecular cyclization were achieved with Cu nanowire felt relative to carbon paper.

Metal nanowire felts can also be used to improve the performance of Li batteries [94,97,108–110]. Active materials with a large capacity for lithium ions usually suffer from a volume change that quickly degrades the capacity. The large voids in a nanowire composite electrode of Cu and Si nanowires could accommodate the volume change of the Si active material upon Li intercalation while retaining electrical contact, thereby improving the retention of capacity [109]. In Li metal batteries, a current collector made of metal nanowires [94,97,108] has been shown to suppress the growth of Li dendrites, which often results in short circuiting and irreversible consumption of Li [111]. In one example, Li deposition mainly took place in the voids of a 3D Cu nanowire network, preventing Li dendrite formation [97]. As a result, a stable columbic efficiency over 200 cycles ($\sim 98.6\%$) was achieved with the nanowire network, while the columbic efficiency for Cu foil dropped to 50% in 40 cycles.

Conclusion and outlook

This review introduced ways in which the unique structure and morphology of nanowires can be used to improve electrochemical processes. Metal nanowires can improve electrocatalytic activity and durability because of their ability to host numerous surface defects and resist degradation. Further improvements in their properties would be greatly aided by computer

simulations that can guide experiments to produce a desired alloy composition and defect structure, as well as the ability to synthesize such structures with high precision at large scales. There remains a huge number of electrochemical reactions in which the properties of nanowires have not been tested. Most metal nanowires from solution-phase syntheses are produced in the presence of shape-directing agents, but there is little research on how such agents affect the electrochemical performance of nanowires. It is likely that the performance of nanowire catalysts would be improved by a cleaning step that is similar to that which is used for cleaning nanoparticles [112]. Nanowires can also be filtered from solution to create 3D flow-through electrodes with the highest specific surface areas and mass transport coefficients reported to date. Future work can focus on creating nanowire felts from more durable materials that can withstand the oxidizing conditions widely used in electro-organic syntheses. The large pore volume of 3D nanowire electrodes has facilitated improvements in capacity retention for lithium ion and lithium metal batteries. Further improvements may result from examining how the aspect ratio of metal nanowires, and thus the porosity of the electrode, impacts battery performance. Overall, metal nanowires offer a new opportunity for researchers to design and synthesize optimal electrode structures from the atomic scale to the microscale, but the design rules have yet to be written.

Conflicts of interest statement

Nothing declared.

Acknowledgements

This work was supported by NSF (United States) Grant No. CHE-1808108.

References

Papers of particular interest, published within the period of review, have been highlighted as:

- of special interest
 - of outstanding interest
1. Possin GE: **A method for forming very small diameter wires.** *Rev Sci Instrum* 1970, **41**:772–774, <https://doi.org/10.1063/1.1684640>.
 2. Bartlett PN, Beanland R, Burt J, Hasan MM, Hector AL, Kashitban RJ, Levason W, Lodge AW, Marks S, Naik J, Rind A, Reid G, Richardson PW, Sloan J, Smith DC: **Exploration of the smallest diameter tin nanowires achievable with electrodeposition: sub 7 nm Sn nanowires produced by electrodeposition from a supercritical fluid.** *Nano Lett* 2018, **18**:941–947, <https://doi.org/10.1021/acs.nanolett.7b04330>.
 3. Zsurzsa S, Pellicer E, Sort J, Péter L, Bakonyi I: **Electron microscopy characterization of electrodeposited homogeneous and multilayered nanowires in the Ni-Co-Cu system.** *J Electrochem Soc* 2018, **165**:D536–D542, <https://doi.org/10.1149/2.0571811jes>.
 4. Xia Y, Yang P, Sun Y, Wu Y, Mayers B, Gates B, Yin Y, Kim F, Yan H: **One-dimensional nanostructures: synthesis, characterization, and applications.** *Adv Mater* 2003, **15**:353–389, <https://doi.org/10.1002/adma.200390087>.
 5. Li S, Chen Y, Huang L, Pan D: **Large-scale synthesis of well-dispersed copper nanowires in an electric pressure cooker and their application in transparent and conductive networks.** *Inorg Chem* 2014, **53**:4440–4444, <https://doi.org/10.1021/ic500094b>.
 6. Cruz MA, Ye S, Kim MJ, Reyes C, Yang F, Flowers PF, Wiley BJ: **Multigram synthesis of Cu-Ag core-shell nanowires enables the production of a highly conductive polymer filament for 3D printing electronics.** *Part Part Syst Char* 2018, **35**:1700385, <https://doi.org/10.1002/ppsc.201700385>.
 7. Niu G, Zhang L, Ruditskiy A, Wang L, Xia Y: **A droplet-reactor system capable of automation for the continuous and scalable production of noble-metal nanocrystals.** *Nano Lett* 2018, **18**:3879–3884, <https://doi.org/10.1021/acs.nanolett.8b01200>.
 8. Niu Z, Cui F, Kuttner E, Xie C, Chen H, Sun Y, Dehestani A, Schierle-Armdt K, Yang P: **Synthesis of silver nanowires with reduced diameters using benzoic acid-derived radicals to make transparent conductors with high transparency and low haze.** *Nano Lett* 2018, **18**:5329–5334, <https://doi.org/10.1021/acs.nanolett.8b02479>.
 9. da Silva RR, Yang M, Choi S-I, Chi M, Luo M, Zhang C, Li Z-Y, Camargo PHC, Ribeiro SJL, Xia Y: **Facile synthesis of sub-20 nm silver nanowires through a bromide-mediated polyol method.** *ACS Nano* 2016, **10**:7892–7900, <https://doi.org/10.1021/acsnano.6b03806>.
 10. Scarabelli L, Grzelczak M, Liz-Marzán LM: **Tuning gold nanorod synthesis through prereduction with salicylic acid.** *Chem Mater* 2013, **25**:4232–4238, <https://doi.org/10.1021/cm402177b>.
 11. Lohse SE, Murphy CJ: **The quest for shape control: a history of gold nanorod synthesis.** *Chem Mater* 2013, **25**:1250–1261, <https://doi.org/10.1021/cm303708p>.
 12. Chang H-H, Murphy CJ: **Mini gold nanorods with tunable plasmonic peaks beyond 1000 nm.** *Chem Mater* 2018, **30**:1427–1435, <https://doi.org/10.1021/acs.chemmater.7b05310>.
 13. Smith DK, Korgel BA: **The importance of the CTAB surfactant on the colloidal seed-mediated synthesis of gold nanorods.** *Langmuir* 2008, **24**:644–649, <https://doi.org/10.1021/la703625a>.
 14. Jin M, He G, Zhang H, Zeng J, Xie Z, Xia Y: **Shape-controlled synthesis of copper nanocrystals in an aqueous solution with glucose as a reducing agent and hexadecylamine as a capping agent.** *Angew Chem Int Ed* 2011, **50**:10560–10564, <https://doi.org/10.1002/anie.201105539>.
 15. Chang Y, Lye ML, Zeng HC: **Large-scale synthesis of high-quality ultralong copper nanowires.** *Langmuir* 2005, **21**:3746–3748, <https://doi.org/10.1021/la050220w>.
 16. Cui F, Yu Y, Dou L, Sun J, Yang Q, Schildknecht C, Schierle-Armdt K, Yang P: **Synthesis of ultrathin copper nanowires using tris(trimethylsilyl)silane for high-performance and low-haze transparent conductors.** *Nano Lett* 2015, **15**:7610–7615, <https://doi.org/10.1021/acs.nanolett.5b03422>.
 17. Kim MJ, Alvarez S, Yan T, Tadepalli V, Fichthorn KA, Wiley BJ: **Modulating the growth rate, aspect ratio, and yield of copper nanowires with alkylamines.** *Chem Mater* 2018, **30**:2809–2818, <https://doi.org/10.1021/acs.chemmater.8b00760>.
 18. Xiong Y, Cai H, Wiley BJ, Wang J, Kim MJ, Xia Y: **Synthesis and mechanistic study of palladium nanobars and nanorods.** *J Am Chem Soc* 2007, **129**:3665–3675, <https://doi.org/10.1021/ja0688023>.
 19. Huang X, Zheng N: **One-pot, high-yield synthesis of 5-fold twinned Pd nanowires and nanorods.** *J Am Chem Soc* 2009, **131**:4602–4603, <https://doi.org/10.1021/ja9009343>.
 20. Xia BY, Wu HB, Yan Y, Lou XW, Wang X: **Ultrathin and ultralong single-crystal platinum nanowire assemblies with highly stable electrocatalytic activity.** *J Am Chem Soc* 2013, **135**:9480–9485, <https://doi.org/10.1021/ja402955t>.
 21. Koenigsman C, Zhou WP, Adzic RR, Sutter E, Wong SS: **Size-dependent enhancement of electrocatalytic performance in relatively defect-free, processed ultrathin platinum nanowires.** *Nano Lett* 2010, **10**:2806–2811, <https://doi.org/10.1021/nl100718k>.

22. Liu Z, Li S, Yang Y, Peng S, Hu Z, Qian Y: **Complex-surfactant-assisted hydrothermal route to ferromagnetic nickel nanobelts.** *Adv Mater* 2003, **15**:1946–1948, <https://doi.org/10.1002/adma.200305663>.
23. Wang Y, Herricks T, Xia Y: **Single crystalline nanowires of lead can be synthesized through thermal decomposition of lead acetate in ethylene glycol.** *Nano Lett* 2003, **3**:1163–1166, <https://doi.org/10.1021/nl034398j>.
24. Wang Y, Jiang X, Herricks T, Xia Y: **Single crystalline nanowires of lead: large-scale synthesis, mechanistic studies, and transport measurements.** *J Phys Chem B* 2004, **108**: 8631–8640, <https://doi.org/10.1021/jp036758x>.
25. Lee J-Y, Connor ST, Cui Y, Peumans P: **Solution-processed metal nanowire mesh transparent electrodes.** *Nano Lett* 2008, **8**:689–692, <https://doi.org/10.1021/nl073296g>.
26. Niu Z, Cui F, Yu Y, Becknell N, Sun Y, Khanarian G, Kim D, Dou L, Dehestani A, Schierle-Arndt K, Yang P: **Ultrathin epitaxial Cu@Au core-shell nanowires for stable transparent conductors.** *J Am Chem Soc* 2017, **139**:7348–7354, <https://doi.org/10.1021/jacs.7b02884>.
27. Cho S, Kang S, Pandya A, Shanker R, Khan Z, Lee Y, Park J, Craig SL, Ko H: **Large-area cross-aligned silver nanowire electrodes for flexible, transparent, and force-sensitive mechanochromic touch screens.** *ACS Nano* 2017, **11**: 4346–4357, <https://doi.org/10.1021/acsnano.7b01714>.
28. Kim KK, Hong S, Cho HM, Lee J, Suh YD, Ham J, Ko SH: **Highly sensitive and stretchable multidimensional strain sensor with prestrained anisotropic metal nanowire percolation networks.** *Nano Lett* 2015, **15**:5240–5247, <https://doi.org/10.1021/acs.nanolett.5b01505>.
29. Choi S, Han SI, Jung D, Hwang HJ, Lim C, Bae S, Park OK, Tschabrunn CM, Lee M, Bae SY, Yu JW, Ryu JH, Lee S-W, Park K, Kang PM, Lee WB, Nezafer R, Hyeon T, Kim D-H: **Highly conductive, stretchable and biocompatible Ag–Au core–sheath nanowire composite for wearable and implantable bioelectronics.** *Nat Nanotechnol* 2018, **13**:1048–1056, <https://doi.org/10.1038/s41565-018-0226-8>.
30. Huang X, Neretina S, El-Sayed MA: **Gold nanorods: from synthesis and properties to biological and biomedical applications.** *Adv Mater* 2009, **21**:4880–4910, <https://doi.org/10.1002/adma.200802789>.
31. Li N, Zhao P, Astruc D: **Anisotropic gold nanoparticles: synthesis, properties, applications, and toxicity.** *Angew Chem Int Ed* 2014, **53**:1756–1789, <https://doi.org/10.1002/anie.201300441>.
32. Yang X, Yang M, Pang B, Vara M, Xia Y: **Gold nanomaterials at work in biomedicine.** *Chem Rev* 2015, **115**:10410–10488, <https://doi.org/10.1021/acs.chemrev.5b00193>.
33. García I, Sánchez-Iglesias A, Henriksen-Lacey M, Grzelczak M, Penadés S, Liz-Marzán LM: **Glycans as biofunctional ligands for gold nanorods: stability and targeting in protein-rich media.** *J Am Chem Soc* 2015, **137**:3686–3692, <https://doi.org/10.1021/jacs.5b01001>.
34. Murphy CJ, Gole AM, Hunyadi SE, Stone JW, Sisco PN, Alkilany A, Kinard BE, Hankins P: **Chemical sensing and imaging with metallic nanorods.** *Chem Commun* 2008:544–557, <https://doi.org/10.1039/b711069c>.
35. Ali MRK, Wu Y, Han T, Zang X, Xiao H, Tang Y, Wu R, Fernández FM, El-Sayed MA: **Simultaneous time-dependent surface-enhanced Raman spectroscopy, metabolomics, and proteomics reveal cancer cell death mechanisms associated with gold nanorod photothermal therapy.** *J Am Chem Soc* 2016, **138**:15434–15442, <https://doi.org/10.1021/jacs.6b08787>.
36. Wei H, Pan D, Zhang S, Li Z, Li Q, Liu N, Wang W, Xu H: **Plasmon waveguiding in nanowires.** *Chem Rev* 2018, **118**: 2882–2926, <https://doi.org/10.1021/acs.chemrev.7b00441>.
37. Zhu W, Zhang Y-J, Zhang H, Lv H, Li Q, Michalsky R, Peterson AA, Sun S: **Active and selective conversion of CO₂ to CO on ultrathin Au nanowires.** *J Am Chem Soc* 2014, **136**: 16132–16135, <https://doi.org/10.1021/ja5095099>.
38. Zheng J, Cullen DA, Forest RV, Wittkopf JA, Zhuang Z, Sheng W, Chen JG, Yan Y: **Platinum-ruthenium nanotubes and platinum-ruthenium coated copper nanowires as efficient catalysts for electro-oxidation of methanol.** *ACS Catal* 2015, **5**:1468–1474, <https://doi.org/10.1021/cs501449y>.
39. Alia SM, Jensen KO, Pivovar BS, Yan Y: **Platinum-coated palladium nanotubes as oxygen reduction reaction electrocatalysts.** *ACS Catal* 2012, **2**:858–863, <https://doi.org/10.1021/cs200682c>.
40. Guo S, Zhang S, Su D, Sun S: **Seed-mediated synthesis of core/shell FePtM/FePt (M = Pd, Au) nanowires and their electrocatalysis for oxygen reduction reaction.** *J Am Chem Soc* 2013, **135**:13879–13884, <https://doi.org/10.1021/ja406091p>.
41. Koenigsman C, Santulli AC, Gong K, Vukmirovic MB, Zhou WP, Sutter E, Wong SS, Adzic RR: **Enhanced electrocatalytic performance of processed, ultrathin, supported Pd-Pt core-shell nanowire catalysts for the oxygen reduction reaction.** *J Am Chem Soc* 2011, **133**:9783–9795, <https://doi.org/10.1021/ja111130t>.
42. Li H-H, Ma S-Y, Fu Q-Q, Liu X-J, Wu L, Yu S-H: **Scalable bromide-triggered synthesis of Pd@Pt core-shell ultrathin nanowires with enhanced electrocatalytic performance toward oxygen reduction reaction.** *J Am Chem Soc* 2015, **137**: 7862–7868, <https://doi.org/10.1021/jacs.5b03877>.
43. Wittkopf JA, Zheng J, Yan Y: **High-performance dealloyed PtCu/CuNW oxygen reduction reaction catalyst for proton exchange membrane fuel cells.** *ACS Catal* 2014, **4**:3145–3151, <https://doi.org/10.1021/cs500692y>.
44. Xiong Y, Siekkinen AR, Wang J, Yin Y, Kim MJ, Xia Y: **Synthesis of silver nanoplates at high yields by slowing down the polyol reduction of silver nitrate with polyacrylamide.** *J Mater Chem* 2007, **17**:2600–2602, <https://doi.org/10.1039/b705253g>.
45. Kim MJ, Alvarez S, Chen Z, Fichthorn KA, Wiley BJ: **Single-crystal electrochemistry reveals why metal nanowires grow.** *J Am Chem Soc* 2018, **140**:14740–14746, <https://doi.org/10.1021/jacs.8b08053>.
46. Kim MJ, Flowers PF, Stewart IE, Ye S, Baek S, Kim JJ, Wiley BJ: **Ethylenediamine promotes Cu nanowire growth by inhibiting oxidation of Cu(111).** *J Am Chem Soc* 2017, **139**:277–284, <https://doi.org/10.1021/jacs.6b10653>.
47. Liao H-G, Cui L, Whitelam S, Zheng H: **Real-time imaging of Pt₃Fe nanorod growth in solution.** *Science* 2012, **336**: 1011–1014, <https://doi.org/10.1126/science.1219185>.
48. Peng Z, You H, Yang H: **Composition-dependent formation of platinum silver nanowires.** *ACS Nano* 2010, **4**:1501–1510, <https://doi.org/10.1021/nn9016795>.
49. Ma Y, Gao W, Shan H, Chen W, Shang W, Tao P, Song C, Addiego C, Deng T, Pan X, Wu J: **Platinum-based nanowires as active catalysts toward oxygen reduction reaction: in situ observation of surface-diffusion-assisted, solid-state oriented attachment.** *Adv Mater* 2017, **29**:1703460, <https://doi.org/10.1002/adma.201703460>.
50. Liang H, Zhao H, Rossouw D, Wang W, Xu H, Botton GA, Ma D: **Silver nanorice structures: oriented attachment-dominated growth, high environmental sensitivity, and real-space visualization of multipolar resonances.** *Chem Mater* 2012, **24**: 2339–2346, <https://doi.org/10.1021/cm3006875>.
51. Zhu C, Peng H-C, Zeng J, Liu J, Gu Z, Xia Y: **Facile synthesis of gold wavy nanowires and investigation of their growth mechanism.** *J Am Chem Soc* 2012, **134**:20234–20237, <https://doi.org/10.1021/ja3091214>.
52. Jiang K, Zhao D, Guo S, Zhang X, Zhu X, Guo J, Lu G, Huang X: **Efficient oxygen reduction catalysis by subnanometer Pt alloy nanowires.** *Sci Adv* 2017, **3**:e1601705, <https://doi.org/10.1126/sciadv.1601705>.
53. Yu Y, Cui F, Sun J, Yang P: **Atomic structure of ultrathin gold nanowires.** *Nano Lett* 2016, **16**:3078–3084, <https://doi.org/10.1021/acs.nanolett.6b00233>.
54. Chang F, Shan S, Petkov V, Skeete Z, Lu A, Ravid J, Wu J, Luo J, Yu G, Ren Y, Zhong C-J: **Composition tunability and (111)-**

- dominant facets of ultrathin platinum-gold alloy nanowires toward enhanced electrocatalysis. *J Am Chem Soc* 2016, **138**: 12166–12175, <https://doi.org/10.1021/jacs.6b05187>.**
55. Li M, Zhao Z, Cheng T, Fortunelli A, Chen C-Y, Yu R, Zhang Q, Gu L, Merinov BV, Lin Z, Zhu E, Yu T, Jia Q, Guo J, Zhang L, Goddard III WA, Huang Y, Duan X: **Ultrafine jagged platinum nanowires enable ultrahigh mass activity for the oxygen reduction reaction.** *Science* 2016, **354**:1414–1419, <https://doi.org/10.1126/science.aaf9050>.
- Demonstrates how the high defect density on Pt nanowires can improve their electrocatalytic activity for oxygen reduction
56. Huang H, Li K, Chen Z, Luo L, Gu Y, Zhang D, Ma C, Si R, Yang J, Peng Z, Zeng J: **Achieving remarkable activity and durability toward oxygen reduction reaction based on ultrathin Rh-doped Pt nanowires.** *J Am Chem Soc* 2017, **139**: 8152–8159, <https://doi.org/10.1021/jacs.7b01036>.
57. Li K, Li X, Huang H, Luo L, Li X, Yan X, Ma C, Si R, Yang J, Zeng J: **One-nanometer-thick PtNiRh trimetallic nanowires with enhanced oxygen reduction electrocatalysis in acid media: integrating multiple advantages into one catalyst.** *J Am Chem Soc* 2018, **140**:16159–16167, <https://doi.org/10.1021/jacs.8b08836>.
- Introduces a synthesis of 1-nm-thick PtNiRh nanowires and shows how alloying improved their electrocatalytic activity and durability for oxygen reduction
58. Liu Z, Qi J, Liu M, Zhang S, Fan Q, Liu H, Liu K, Zheng H, Yin Y, Gao C: **Aqueous synthesis of ultrathin platinum/non-noble metal alloy nanowires for enhanced hydrogen evolution activity.** *Angew Chem* 2018, **130**:11852–11856, <https://doi.org/10.1002/ange.201806194>.
59. Zhang N, Bu L, Guo S, Guo J, Huang X: **Screw thread-like platinum-copper nanowires bounded with high-index facets for efficient electrocatalysis.** *Nano Lett* 2016, **16**:5037–5043, <https://doi.org/10.1021/acs.nanolett.6b01825>.
60. Jiang X, Qiu X, Fu G, Sun J, Huang Z, Sun D, Xu L, Zhou J, Tang Y: **Highly simple and rapid synthesis of ultrathin gold nanowires with (111)-dominant facets and enhanced electrocatalytic properties.** *J Mater Chem A* 2018, **6**:17682–17687, <https://doi.org/10.1039/c8ta06676k>.
61. Zhang N, Zhu Y, Shao Q, Zhu X, Huang X: **Ternary PtNi/Pt_xPb/Pt core/multishell nanowires as efficient and stable electrocatalysts for fuel cell reactions.** *J Mater Chem A* 2017, **5**: 18977–18983, <https://doi.org/10.1039/c7ta05130a>.
62. Alia SM, Shulda S, Ngo C, Pylypenko S, Pivovar BS: **Iridium-based nanowires as highly active, oxygen evolution reaction electrocatalysts.** *ACS Catal* 2018, **8**:2111–2120, <https://doi.org/10.1021/acscatal.7b03787>.
- Introduces a synthesis for Ir-based nanowires from galvanic displacement of Ni and Co nanowires and their use for the oxygen evolution reaction.
63. Ji L, Wang Z, Wang H, Shi X, Asiri AM, Sun X: **Hierarchical CoTe₂ nanowire array: an effective oxygen evolution catalyst in alkaline media.** *ACS Sustain Chem Eng* 2018, **6**:4481–4485, <https://doi.org/10.1021/acssuschemeng.7b04309>.
64. Zhao L, Cao Q, Wang A, Duan J, Zhou W, Sang Y, Liu H: **Iron oxide embedded titania nanowires – an active and stable electrocatalyst for oxygen evolution in acidic media.** *Nano Energy* 2018, **45**:118–126, <https://doi.org/10.1016/j.nanoen.2017.12.029>.
65. Lv H, Chen X, Xu D, Hu Y, Zheng H, Suib SL, Liu B: **Ultrathin PdPt bimetallic nanowires with enhanced electrocatalytic performance for hydrogen evolution reaction.** *Appl Catal B* 2018, **238**:525–532, <https://doi.org/10.1016/j.apcatb.2018.07.060>.
66. Zou P, Li J, Zhang Y, Liang C, Yang C, Fan HJ: **Magnetic-field-induced rapid synthesis of defect-enriched Ni-Co nanowire membrane as highly efficient hydrogen evolution electrocatalyst.** *Nano Energy* 2018, **51**:349–357, <https://doi.org/10.1016/j.nanoen.2018.06.080>.
67. Zhang C, Liu S, Mao Z, Liang X, Chen B: **Ag-Ni core-shell nanowires with superior electrocatalytic activity for alkaline hydrogen evolution reaction.** *J Mater Chem A* 2017, **5**: 16646–16652, <https://doi.org/10.1039/c7ta04220e>.
68. Chen R, Sun M, Pang G, Zhou J, Hou L, Gao F: **Highly active PdCu alloy nanowire network electrocatalyst for ethanol and methanol electrooxidation.** *ChemElectroChem* 2017, **4**: 1081–1087, <https://doi.org/10.1002/celec.201700058>.
69. Wang J, Zhang P, Xiahou Y, Wang D, Xia H, Mõhwald H: **Simple synthesis of Au-Pd alloy nanowire networks as macroscopic, flexible electrocatalysts with excellent performance.** *ACS Appl Mater Interfaces* 2018, **10**:602–613, <https://doi.org/10.1021/acsami.7b14955>.
70. Wang P, Zhang Y, Shi R, Wang Z: **Trimetallic PtPdCu nanowires as an electrocatalyst for methanol and formic acid oxidation.** *New J Chem* 2018, **42**:19083–19089, <https://doi.org/10.1039/c8nj04723e>.
71. Hong W, Wang J, Wang E: **Facile synthesis of PtCu nanowires with enhanced electrocatalytic activity.** *Nano Res* 2015, **8**: 2308–2316, <https://doi.org/10.1007/s12274-015-0741-y>.
72. Liao Y, Yu G, Zhang Y, Guo T, Chang F, Zhong C-J: **Composition-tunable PtCu alloy nanowires and electrocatalytic synergy for methanol oxidation reaction.** *J Phys Chem C* 2016, **120**:10476–10484, <https://doi.org/10.1021/acs.jpcc.6b02630>.
73. Rana M, Patil PK, Chhetri M, Dileep K, Datta R, Gautam UK: **Pd-Pt alloys nanowires as support-less electrocatalyst with high synergistic enhancement in efficiency for methanol oxidation in acidic medium.** *J Colloid Interface Sci* 2016, **463**:99–106, <https://doi.org/10.1016/j.jcis.2015.10.042>.
74. Guo T, Yu G, Zhang Y, Xiang H, Chang F, Zhong C-J: **Synthesis of ultralong, monodispersed, and surfactant-free gold nanowire catalysts: growth mechanism and electrocatalytic properties for methanol oxidation reaction.** *J Phys Chem C* 2017, **121**:3108–3116, <https://doi.org/10.1021/acs.jpcc.6b11608>.
75. Ma S-Y, Li H-H, Hu B-C, Cheng X, Fu Q-Q, Yu S-H: **Synthesis of Pt-based quaternary PtPdRuTe nanotubes with optimized incorporation of Pd for enhanced electrocatalytic activity.** *J Am Chem Soc* 2017, **139**:5890–5895, <https://doi.org/10.1021/jacs.7b01482>.
- Reports the synthesis of Pt-based nanotubes from Te nanowires via galvanic displacement and the effect of nanowire composition on their activity for methanol oxidation.
76. Zhu M, Shao Q, Pi Y, Guo J, Huang B, Qian Y, Huang X: **Ultrathin vein-like iridium-tin nanowires with abundant oxidized tin as high-performance ethanol oxidation electrocatalysts.** *Small* 2017, **13**:1701295, <https://doi.org/10.1002/sml.201701295>.
77. Liu W, Haubold D, Rutkowski B, Oschatz M, Hübner R, Werheid M, Ziegler C, Sonntag L, Liu S, Zheng Z, Herrmann A-K, Geiger D, Terlan B, Gemming T, Borchardt L, Kaskel S, Czyrka-Filemonowicz A, Eychmüller A: **Self-supporting hierarchical porous PtAg alloy nanotubular aerogels as highly active and durable electrocatalysts.** *Chem Mater* 2016, **28**:6477–6483, <https://doi.org/10.1021/acs.chemmater.6b01394>.
- Demonstrates a method for fabricating PtAg nanotubular aerogels and their excellent electrocatalytic activity and durability for formic acid oxidation.
78. Huang H, Ruditskiy A, Choi S-I, Zhang L, Liu J, Ye Z, Xia Y: **One-pot synthesis of penta-twinned palladium nanowires and their enhanced electrocatalytic properties.** *ACS Appl Mater Interfaces* 2017, **9**:31203–31212, <https://doi.org/10.1021/acsami.7b12018>.
79. Jiang X, Fu G, Wu X, Liu Y, Zhang M, Sun D, Xu L, Tang Y: **Ultrathin AgPt alloy nanowires as a high-performance electrocatalyst for formic acid oxidation.** *Nano Res* 2018, **11**: 499–510, <https://doi.org/10.1007/s12274-017-1658-4>.
80. Li Y, Cui F, Ross MB, Kim D, Sun Y, Zhang P: **Structure-sensitive CO₂ electroreduction to hydrocarbons on ultrathin 5-fold twinned copper nanowires.** *Nano Lett* 2017, **17**:1312–1317, <https://doi.org/10.1021/acs.nanolett.6b05287>.
- Demonstrates how the atomic structure of pentagonally-twinned Cu nanowires can promote a high methane selectivity for electrochemical CO₂ reduction.
81. Liu H, Xiang K, Liu Y, Zhu F, Zou M, Yan X, Chai L: **Polydopamine functionalized Cu nanowires for enhanced CO₂**

- electroreduction towards methane.** *ChemElectroChem* 2018, 5:3991–3999, <https://doi.org/10.1002/celec.201801132>.
82. Liu R, Zhao H, Zhao X, He Z, Lai Y, Shan W, Bekana D, Li G, Liu J: **Defect sites in ultrathin Pd nanowires facilitate the highly efficient electrochemical hydrodechlorination of pollutants by H_{ads}.** *Environ Sci Technol* 2018, 52:9992–10002, <https://doi.org/10.1021/acs.est.8b02740>.
 83. Kuhl KP, Cave ER, Abram DN, Jaramillo TF: **New insights into the electrochemical reduction of carbon dioxide on metallic copper surfaces.** *Energy Environ Sci* 2012, 5:7050–7059, <https://doi.org/10.1039/c2ee21234j>.
 84. Luo M, Guo S: **Strain-controlled electrocatalysis on multimetallic nanomaterials.** *Nat Rev Mater* 2017, 2:17059, <https://doi.org/10.1038/natrevmats.2017.59>.
 85. Zhou M, Wang H, Vara M, Hood ZD, Luo M, Yang TH, Bao S, Chi M, Xiao P, Zhang Y, Xia Y: **Quantitative analysis of the reduction kinetics responsible for the one-pot synthesis of Pd-Pt bimetallic nanocrystals with different structures.** *J Am Chem Soc* 2016, 138:12263–12270, <https://doi.org/10.1021/jacs.6b07213>.
 86. Luo L, Duan Z, Li H, Kim J, Henkelman G, Crooks RM: **Tunability of the adsorbate binding on bimetallic alloy nanoparticles for the optimization of catalytic hydrogenation.** *J Am Chem Soc* 2017, 139:5538–5546, <https://doi.org/10.1021/jacs.7b01653>.
 87. Gloag L, Benedetti TM, Cheong S, Marjo CE, Gooding JJ, Tilley RD: **Cubic-core hexagonal-branch mechanism to synthesize bimetallic branched and faceted Pd-Ru nanoparticles for oxygen evolution reaction electrocatalysis.** *J Am Chem Soc* 2018, 140:12760–12764, <https://doi.org/10.1021/jacs.8b09402>.
 88. Li W, Amiin IS, Ye B, Wang Z, Zhu J, Kou Z, Mu S: **TePtFe nanotubes as high-performing bifunctional electrocatalysts for the oxygen reduction reaction and hydrogen evolution reaction.** *ChemSusChem* 2018, 11:1328–1333, <https://doi.org/10.1002/cssc.201702403>.
 89. Narayanamoorthy B, Datta KKR, Eswaramoorthy M, Balaji S: **Highly active and stable Pt₃Rh nanoclusters as supportless electrocatalyst for methanol oxidation in direct methanol fuel cells.** *ACS Catal* 2014, 4:3621–3629, <https://doi.org/10.1021/cs500628m>.
 90. Young AP, Colbow V, Harvey D, Rogers E, Wessel S: **A semi-empirical two step carbon corrosion reaction model in PEM fuel cells.** *J Electrochem Soc* 2013, 160:F381–F388, <https://doi.org/10.1149/2.061304jes>.
 91. Liang HW, Cao X, Zhou F, Cui CH, Zhang WJ, Yu SH: **A free-standing Pt-nanowire membrane as a highly stable electrocatalyst for the oxygen reduction reaction.** *Adv Mater* 2011, 23:1467–1471, <https://doi.org/10.1002/adma.201004377>.
 92. Chen Z, Waje M, Li W, Yan Y: **Supportless Pt and PtPd nanotubes as electrocatalysts for oxygen-reduction reactions.** *Angew Chem Int Ed* 2007, 119:4138–4141, <https://doi.org/10.1002/anie.200700894>.
 93. Catenacci MJ, Reyes C, Cruz MA, Wiley BJ: **Stretchable conductive composites from Cu-Ag nanowire felt.** *ACS Nano* 2018, 12:3689–3698, <https://doi.org/10.1021/acsnano.8b00887>.
 94. Xue P, Liu S, Shi X, Sun C, Lai C, Zhou Y, Sui D, Chen Y, Liang J: **A hierarchical silver-nanowire-graphene host enabling ultrahigh rates and superior long-term cycling of lithium-metal composite anodes.** *Adv Mater* 2018, 30:1804165, <https://doi.org/10.1002/adma.201804165>.
 95. Zankowski SP, Vereecken PM: **Combining high porosity with high surface area in flexible interconnected nanowire meshes for hydrogen generation and beyond.** *ACS Appl Mater Interfaces* 2018, 10:44634–44644, <https://doi.org/10.1021/acsaami.8b15888>.
 96. Graves JE, Bowker MEA, Summer A, Greenwood A, Ponce de León C, Walsh FC: **A new procedure for the template synthesis of metal nanowires.** *Electrochem Commun* 2018, 87:58–62, <https://doi.org/10.1016/j.elecom.2017.11.022>.
 97. Lu L-L, Ge J, Yang J-N, Chen S-M, Yao H-B, Zhou F, Yu S-H: **Free-standing copper nanowire network current collector for improving lithium anode performance.** *Nano Lett* 2016, 16:4431–4437, <https://doi.org/10.1021/acs.nanolett.6b01581>.
Demonstrates the suppression of Li dendrite growth with a 3D Cu nanowire network current collector.
 98. Parkhouse JG, Kelly A: **The random packing of fibers in three dimensions.** *Proc R Soc A* 1995, 451:737–746, <https://doi.org/10.1098/rspa.1995.0152>.
 99. Weber AZ, Mench MM, Meyers JP, Ross PN, Gostick JT, Liu Q: **Redox flow batteries: a review.** *J Appl Electrochem* 2011, 41:1137–1164, <https://doi.org/10.1007/s10800-011-0348-2>.
 100. Leung P, Li X, Ponce De León C, Berlouis L, Low CTJ, Walsh FC: **Progress in redox flow batteries, remaining challenges and their applications in energy storage.** *RSC Adv* 2012, 2:10125–10156, <https://doi.org/10.1039/c2ra21342g>.
 101. Martínez-Huitle CA, Rodrigo MA, Sirés I, Scialdone O: **Single and coupled electrochemical processes and reactors for the abatement of organic water pollutants: a critical review.** *Chem Rev* 2015, 115:13362–13407, <https://doi.org/10.1021/acs.chemrev.5b00361>.
 102. Li H, Breen CP, Seo H, Jamison TF, Fang Y-Q, Bio MM: **Ni-catalyzed electrochemical decarboxylative C-C couplings in batch and continuous flow.** *Org Lett* 2018, 20:1338–1341, <https://doi.org/10.1021/acs.orglett.8b00070>.
 103. Mo Y, Jensen KF: **Continuous N-hydroxyphthalimide (NHPI)-Mediated electrochemical aerobic oxidation of benzylic C-H bonds.** *Chem Eur J* 2018, 24:10260–10265, <https://doi.org/10.1002/chem.201802588>.
 104. Pletcher D, Green RA, Brown RCD: **Flow electrolysis cells for the synthetic organic chemistry laboratory.** *Chem Rev* 2018, 118:4573–4591, <https://doi.org/10.1021/acs.chemrev.7b00360>.
Review summarizing flow electrochemistry methods for electroorganic synthesis.
 105. Schmal D, Van Erkel J, Van Duin PJ: **Mass transfer at carbon fibre electrodes.** *J Appl Electrochem* 1986, 16:422–430, <https://doi.org/10.1007/BF01008853>.
 106. Delanghe B, Tellier S, Astruc M: **Mass transfer to a carbon or graphite felt electrode.** *Electrochim Acta* 1990, 35:1369–1376, [https://doi.org/10.1016/0013-4686\(90\)85008-B](https://doi.org/10.1016/0013-4686(90)85008-B).
 107. Arenas LF, Ponce de León C, Walsh FC: **Engineering aspects of the design, construction and performance of modular redox flow batteries for energy storage.** *J Energy Storage* 2017, 11:119–153, <https://doi.org/10.1016/j.est.2017.02.007>.
 108. Lu L-L, Zhang Y, Pan Z, Yao H-B, Zhou F, Yu S-H: **Lithiophilic Cu-Ni core-shell nanowire network as a stable host for improving lithium anode performance.** *Energy Storage Mater* 2017, 9:31–38, <https://doi.org/10.1016/j.ensm.2017.06.004>.
 109. Hwang C, Kim T-H, Cho Y-G, Kim J, Song H-K: **All-in-one assembly based on 3d-intertangled and cross-jointed architectures of Si/Cu 1d-nanowires for lithium ion batteries.** *Sci Rep* 2015, 5:8623, <https://doi.org/10.1038/srep08623>.
Describes how a nanowire composite electrode improved the performance of a Li ion battery.
 110. Yin Z, Cho S, You D-J, Ahn Y, Yoo J, Kim YS: **Copper nanowire/multi-walled carbon nanotube composites as all-nanowire flexible electrode for fast-charging/discharging lithium-ion battery.** *Nano Res* 2018, 11:769–779, <https://doi.org/10.1007/s12274-017-1686-0>.
 111. Mukhopadhyay A, Jangid MK: **Li metal battery, heal thyself.** *Science* 2018, 359:1463, <https://doi.org/10.1126/science.aat2452>.
 112. Montiel MA, Vidal-Iglesias FJ, Montiel V, Solla-Gullón J: **Electrocatalysis on shape-controlled metal nanoparticles: progress in surface cleaning methodologies.** *Curr Opin Electrochem* 2017, 1:34–39, <https://doi.org/10.1016/j.coelec.2016.12.007>.